



KAUNAS UNIVERSITY OF TECHNOLOGY
FACULTY OF MECHANICAL ENGINEERING AND DESIGN
RESEARCH CENTRE FOR PLASTIC AND LEATHER PRODUCTS

Studentu str., 56, LT-51424 Kaunas, Lithuania
Tel.: 0037-37 300207, MOBILE: 00370 610 05190, fax: 0037-37 353989
E-mail: midf.pogtc@ktu.lt, virginija.jankauskaite@ktu.lt

Data: 27-06-2014

TEST REPORT
Nr. POGTC-049-06/14

Page 1 of 2

1. CUSTOMER

**KING MINDAUGAS TREINING
CENTER**

Karaliaus Mindaugo avenue 11,
Kaunas, LT-44287 Lithuania

2. MANUFACTURER

T-Tape Company
Hogebergdreef 60,
4645 EX Putte,
The Netherlands

3. SAMPLE DESCRIPTION:

Purpose of testing	Plastics quality assessment
Normative document	—
Destination	Plastic sheets
Type	Turbotreat Comfort TRC20027 0000000
Color	Skin/beige
Perforation	Perforated
Thickness	3.0 mm
Coating	One side coated
Label	

Principal executive

A. Lisauskaite

Centre Manager

V. Jankauskaite

4. Number and date of ordering: 10-06-2014
5. Sample received: 15-06-2014
6. Sample tested 17-06-2014 – 27-06-2014

7. RESULTS OF TEST

Normative reference, section clause	Parameter	Specification requirement	Sample results:	
			range	average
ISO 2781	Density	—	—	1.14 g/cm ³
LST EN ISO 527-1	Elastic modulus	—	—	377 MPa
LST EN ISO 527-2	Tensile strength ¹	—	22.5 – 28.6 MPa	26.2 MPa
LST EN ISO 527-3	Strain at break ¹	—	618 – 989 %	856 %
LST EN ISO 178	Flexural modulus ¹	—	227 – 345 MPa	278 MPa
—	Maximum elongation when activated ²	—	1830 – 2020 %	1925 %

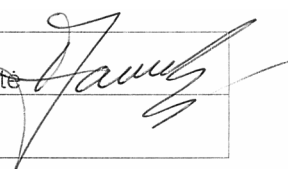
NOTE:

¹ Specimens were cut at various directions (⊥, ||).

² Specimens activation and testing conditions: a) temperature $T = 65 \pm 1^\circ\text{C}$, b) duration $\tau = 2.5$ min; c) testing according to the requirements of standard LST EN ISO 527.

8. OTHER INFORMATION

- 8.1. Test results are valid only for this object.
- 8.2. To reprint or duplicate test report in part without permission of Centre Manager is not allowed.

Principal executive	A. Lisauskaitė 	Centre Manager	V. Jankauskaitė 
---------------------	--	----------------	---